

ISSN 2181-8622

**SCIENTIFIC AND TECHNICAL JOURNAL
OF NAMANGAN INSTITUTE OF ENGINEERING AND
TECHNOLOGY**

**НАМАНГАН МУҲАНДИСЛИК-ТЕХНОЛОГИЯ ИНСТИТУТИ
ИЛМИЙ-ТЕХНИКА ЖУРНАЛИ**

**НАУЧНО-ТЕХНИЧЕСКИЙ ЖУРНАЛ
НАМАНГАНСКОГО ИНЖЕНЕРНО-ТЕХНОЛОГИЧЕСКОГО
ИНСТИТУТА**



The journal is included in the list of scientific publications recommended by the Higher Attestation Commission under the Cabinet of Ministers of the Republic of Uzbekistan for publication of the main scientific results of dissertations in technical sciences in 2019 (Technical Sciences - 05.00.00) №33.

PURIFICATION OF FLUORINE AND SULPHATE IMPURITIES DURING THE EXTRACTION OF PHOSPHORIC ACID AND STUDY OF THE PROCESS OF OBTAINING HIGH-GRADE AMMONIUM PHOSPHATES

Qodirova Gulnoza Qodirjonovna

*Doctoral student of Namangan Engineering Construction Institute
Tel: +99(897) 255 1706, e-mail: guli5067@mail.ru*

Shamshidinov Israiljon Turgunovich

*Doctor of technical sciences, Professor of Namangan Engineering Construction Institute
Tel: +99(898) 150 1661, e-mail: israiljon2010@mail.ru*

Mamadjanov Zokir Nematjanovich

*Associate professor of Namangan Engineering Construction Institute
Tel: +99(891) 351 2155, e-mail: Zokirjon.Mamadjanov.79@mail.ru*

Najmiddinov Rixsitilla Yunusali o'g'li

*Doctoral student of Namangan Engineering Construction Institute
Tel: +99(894) 150 5891, e-mail: najmiddinov9191@gmail.com*

Abstract:

Objective. *The aim of the research is the removal of phosphoric acid from Central Kyzylkum phosphates by fluoride and sulphate additives during the extraction of phosphoric acid, iron and aluminium, calcium, magnesium, sulphate, fluorine during the ammonium phosphate acid extraction phase. Study the process of producing environmentally friendly and fully water-soluble ammonium phosphates.*

Methods. *The study used chemical, physico-chemical (photocolorimetric, pH-metric, electron-microscopic) and statistical processing of experimental data.*

Results. *The continuation of the phosphoric acid extraction process simplifies the process by removing fluorine and sulphate additives, by deep cleaning of iron and aluminium, calcium, magnesium, fluorine and other additives in the produced acid, the main nutrient element in the finished product - P_2O_5 has been achieved.*

Conclusion. *Studies have shown that simultaneous fluorination and desulphurization of EPA based on Central Kyzylkum phosphate can be achieved by adding calcium carbonate or WRPC to the extraction sludge. High-quality water-soluble ammonium phosphates can be obtained by partially purifying phosphoric acid during extraction and complete purification by extracting phosphoric acid with ammonia. The product is a water-soluble nitrogen phosphorus fertilizer and is used as a fertilizer for drip irrigation and for hydroponic cultivation of crops.*

Keywords: *phosphoric acid, extraction phosphoric acid, fertilizer, mineral fertilizer, non-fluorinated fertilizer, complex fertilizer, nitrogen-phosphorus fertilizer, ammonium phosphates, monoammonium phosphate, diammonium phosphate.*

Introduction. *Currently, the global demand for phosphate raw material is 190 million tonnes or 43 million tonnes of P_2O_5 per year. By 2030, demand for phosphate raw materials is projected to increase to 2 million tons. By 2050, the demand for raw materials will reach 220 million tonnes of phosphate, or 70 million tonnes of P_2O_5 [1].*

As a result of large-scale concrete activities in the country, high results have been achieved in scientific research in the production of new types of phosphorus fertilizers based on local raw materials and in the provision of high-quality mineral fertilizers to agriculture.

In the third direction of the Strategy for Action of the Republic of Uzbekistan for 2017-2021 «... accelerated development of high-tech processing industries, primarily production of finished products with high value added based on deep processing of local raw materials. » Important tasks have been identified [2]. In this regard, it is important to create a technology for the production of high quality ammonium phosphates that meet the requirements of drip and hydroponic irrigation.

Therefore, the removal of fluorine and other additives from the product plays a special role in the process. Because fluorine compounds are very harmful to the environment. Research shows that fluorine not only affects plants but also causes many serious diseases in humans and other organisms.

The recovery and use of fluorine from phosphate feedstock solve two problems: increasing the production of fluorine compounds and preventing damage to the biosphere due to the release of fluorine into the environment. Some of the fluorine from the phosphate feedstock is extracted during extraction and the rest is removed by evaporation, granulation and drying. Phosphate extraction is also achieved by neutralizing phosphoric acid with non-fluoric containing components to reduce the relative fraction of fluorine in the product [3, 4, 5].

Many plants absorb large amounts of fluorine. For example, 1 kg of tea contains between 57 and 1,370 mg of fluorine and 4,500 mg [6, 7]. In this process, fluoride accumulates in the seeds of cotton, and most of it becomes cotton oil. Studies show that the content of fluoride in soil increases when fluorine is added to the soil, including mineral fertilizers [8]. In the presence of nitrogen phosphorus potassium fertilizers, the amount of fluorine absorbed by plants increases [9].

Phosphorus fertilizers are the main source of fluorine in soil. For example, apatite and phosphate contain, on average, 3.0% and 2.7% fluoride, respectively. The extracted phosphate acid (EPA) based on phosphate Central Kyzylkum contains about 1.2% fluoride. The method of deposition of acids from alkali metals in the form of silicon fluoride is not very effective as EPA contains almost very small amounts of acid-soluble silicon compounds [10].

When processing natural phosphates, the fluorine contained therein is distributed between the gas, liquid (EPA) and solid (phosphogypse) phases. According to the dihydrate scheme, 80-85% of the phosphoric acid in the raw material (apatite and phosphate) is converted into a hydrofluoric acid, and after processing into fertilizers.

Increasing the production of phosphorus, especially complex fertilizers, to fully meet the demand for agricultural fertilizers creates a risk of fluorine saturation of soils, plants and water bodies [11]. The negative effects of fluorine compounds entering the atmosphere and open water bodies and accumulating in living organisms and flora have been sufficiently studied [8, 9, 12].

Sulphates, chlorides, phosphates, carbonates and sodium and potassium hydroxides are used to precipitate EPA fluorides as compounds of silicon fluoride of insoluble alkali metals [13]. These methods are based on the chemical interaction of the above-mentioned salts with silica in EPA. Fluorine clearance is up to 90%.

The process of purifying EPAs based on Central Kyzylkum phosphate with alkali metal salts is well described in the literature. EPA is first purified from sulphates and then from fluorine. [14]

The authors have studied in detail the process of fluoridation of EPA based on phosphate Central Kyzylkum sulphate, dihydrophosphate, sodium metasilicate and have shown that the degree of fluoridation can be increased from 38-40% to 80-85% and EPA. Desorption technology developed [15, 16].

There are also materials for desulphurization of defluorinated EPAs by unprocessed raw materials of the Central Kyzylkum [17], carbonate and calcium oxide washed with enriched

phosphate [18]. A patent has been obtained for obtaining nutrient sediments by purifying EPA of fluorine and sulphate compounds [19]. However, there are no materials for simultaneous removal of fluoride and sulphate from the extraction pulp when EPA is extracted from the phosphate of the Central Kyzylkum.

Methods. The simultaneous purification of EPA from fluorine and sulphate results in, first, an environmentally friendly product, second, a high contribution of useful substances to the product, third, some coverage of low-grade raw materials, fourth, fluorine - valuable raw materials, joins can be isolated in the process itself. Therefore, research on simultaneously purifying EPA from fluoride and sulphate is relevant.

In order to purify fluorine and other additives in the extracted phosphoric acid and to produce high-quality ammonium phosphates, purification processes for the extraction of phosphoric acid and the neutralization of purified acid with gaseous ammonia were studied.

In the composition for the study, in% by weight: $P_2O_5 = 26,20$; $CO_2 = 3,08$; $CaO = 57,64$; $MgO = 1,07$; $R_2O_3 = 0,79$; $SO_3 = 2,18$; $F = 2,88$; e.v. = 1.54 The washed phosphate concentrate of the Central Kyzylkum (WRPC) is used.

Deposition of fluorine and sulphate from Calcium Carbonate extraction sludge at 60-150% of the calcium oxide fluoride norm and 80-100% of the SO_3 binding norm as calcium sulphate (limestone etc.)) and conducted by WRPC. The process of extraction of phosphoric acid with sulphuric acid was carried out in dihydrate mode, before filtration of the resultant extraction pulp fluorine and free sulphuric acid in it were deposited with calcium carbonate or WRPC.

Ammonia with gaseous ammonia up to $pH = 3.8-5.5$ to obtain relatively pure solutions of pre-purified acid from fluorine and sulphate.


Sulfatlar va ftorning qoldiq miqdori kalsiy ionlari bilan $CaSO_4$ va CaF_2 tarzida, temir va alyuminiy ionlari esa $FePO_4$ va $AlPO_4$ tarzida cho'kadi. Cho'kma dekantatsiyalash yo'li bilan eritmadan ajratiladi.

Residual sulphates and fluorine are deposited with calcium ions as $CaSO_4$ va CaF_2 and iron and aluminium ions are deposited as $FePO_4$ and $AlPO_4$. The sediment is separated from the solution by decantation.


Results. The territory of the republic consists of calcium and magnesium carbonates that meet technological requirements of industrial production: calcite, limestone, dolomite and other local minerals are found in large quantities [20]. In the process of extraction of phosphoric acid with sulphuric acid, the use of local carbonate raw material in fluoridation and desulphurization of extraction suspension is very efficient.

The results of the research are presented in Tables 1, 2 and 3, as well as in Figures 1, 2 and 3.

Discussions. Table 1 shows that when EPA is produced without adding calcium carbonate, 5.45% of all fluorine in phosphate is converted into a gas phase, 40.5% into phosphogypse and 54.05% of fluorine remains in EPA. The following reactions may occur when adding calcium carbonate to the extraction suspension:

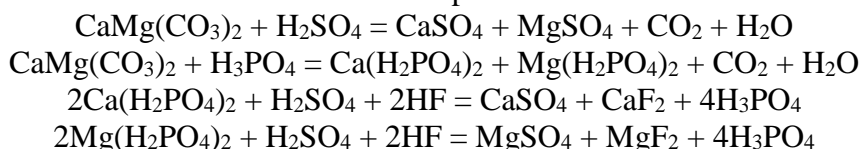

Magnesium fluoride is relatively soluble in acids than calcium fluoride, reacting with strong acids, including sulphuric acid:



magnesium sulfate and hydrogen fluoride.

This process is complex because magnesium monophosphate and sulphate, which are

well soluble in EPA, can react with calcium carbonate to form calcium sulphate monophosphate. However, magnesium carbonate also reacts with phosphoric acid to form magnesium monophosphate. This is confirmed by the fact that the amount of magnesium in the EPA remains constant at 0.80-0.82% (Table 1).

table.1.

Effects of calcium carbonate norm on EPA chemical composition, gas phase and phosphogypso permeability of fluorine, as well as technological parameters of production of fluorinated and desulphurized EPA

Name the indicators	Calcium carbonate content for binding free fluorine in stoichiometry,%						
	-	60	80	100	120	140	150
Standard for calcium carbonate binding free H ₂ SO ₄ to stoichiometry,%	-	80	100	100	100	100	100
EPA chemical composition, heavy. %							
P ₂ O ₅	20,15	20,08	19,97	19,85	20,24	19,94	20,02
CaO	0,41	0,39	0,58	0,94	1,46	2,14	2,61
MgO	0,82	0,81	0,81	0,80	0,82	0,81	0,81
SO ₃	2,22	0,86	0,51	0,48	0,52	0,47	0,44
R ₂ O ₃	0,61	0,61	0,60	0,60	0,59	0,60	0,59
F	1,32	0,69	0,51	0,32	0,27	0,25	0,25
particulate matter	0,25	0,32	0,28	0,19	0,24	0,17	0,16
Fluorine conversion rate, %							
Phosphogypsum	40,5	68,4	74,1	82,5	85,7	86,6	86,8
gaseous phase	5,4	5,3	5,1	4,1	4,2	4,0	4,1
All	45,9	73,7	79,2	86,6	89,9	90,6	90,9
Technological parameters of production of fluorinated and sulfated EPA							
K _{p.} , %	98,7	98,7	98,7	98,6	98,5	98,5	98,4
K _{sep.} , %	95,8	95,7	95,5	95,5	95,6	95,5	95,5
K _{wash.} , %	99,2	99,3	99,3	99,4	99,4	99,4	99,3
K _{prod.} , %	95,0	95,0	94,8	94,9	95,0	94,9	94,8
The density of the porridge (ρ), g/sm ³ , 25°C	1,26	1,26	1,26	1,26	1,26	1,27	1,27
The stickiness of the porridge (η), spz, 25°C	3,31	3,48	3,58	3,61	3,66	3,70	3,72
Extraction porridge filtration rate, kg/m ² ·s	810,11	809,07	808,20	807,41	806,85	806,60	806,46
<i>Size of phosphogypsum crystals, μm</i>	100x24, 120x20, 220x20, more 560x80, 400x80, 360x28 and partially 100x16, 80x60, 60x20						

With the addition of calcium carbonate and the formation of calcium fluoride, the amount of fluorine released into the gas phase decreases from 5.45% to 4.11%, indicating that the bulk of it is released at the beginning of the process. When CaCO₃ is added to the decomposition process at a rate of 100-150%, the total conversion of fluorine to the gas phase and phosphogypsum is 86.6-90.9%. The fluoride content of EPA is 0.25-0.32%, which is 4.1-5.3 times less than in the absence of calcium carbonate. When the CaCO₃ content in CaO is 100-

120%, the EPA degree of fluorination is 75.4-80.5%, and the sulphating rate is 78.7-79.6% (figures 1 and 2). Figures show that adding more than 120% calcium carbonate to the amount of fluorine and sulphate in acid changes very little with the loss of fluoride and sulphate. The amount of fluorine remaining in EPA is 9.1-13.4% of the total phosphate. When the level of calcium carbonate in phosphate changes from 60 to 100%, the additional conversion of fluorine to phosphogypse is 27.9-42.0%. Increasing the level of calcium carbonate by 120-150% increases the conversion of fluorine to the solid phase by only 3.2-4.3%. Excess calcium carbonate from EPA is used in the deposition of fluorine to form calcium sulphate due to the presence of excess sulphuric acid and monocalcium phosphate due to its interaction with phosphoric acid. The data in Table 2 show that the SO₃ content decreased from 2.22% to 0.44-0.52% and the calcium oxide content increased from 0.41% to 2.61%. The decomposition, separation, leaching and yield coefficients range from 60 to 150 per cent for fluorine binding, from 80 to 100 per cent for neutralizing the excess sulphuric acid for normal calcium carbonate 98.4 to 98.7 per cent and 95.5 to 95.8 per cent respectively. 99.2-99.4 per cent and 94.8-95.0 per cent.

table 2

Technological parameters of production of fluorinated and sulphated EPA with WRPC

Name the indicators	WRPC standard for binding free fluorine relative to stoichiometry,%						
	-	60	80	100	120	140	150
MOFK standard for binding free H ₂ SO ₄ to stoichiometry,%	-	80	100	100	100	100	100
Chemical composition of EFK, heavy. %							
P ₂ O ₅	20,15	20,87	21,28	21,13	21,71	21,81	21,89
CaO	0,41	1,04	1,17	1,26	1,55	1,94	2,15
MgO	0,82	0,85	0,86	0,85	0,88	0,89	0,88
SO ₃	2,22	0,90	0,61	0,47	0,48	0,48	0,48
R ₂ O ₃	0,61	0,63	0,64	0,63	0,65	0,66	0,66
F	1,32	0,74	0,56	0,36	0,30	0,31	0,31
particulate matter	0,25	0,34	0,31	0,25	0,27	0,28	0,19

The filtration rate of phosphogypsum is relatively high, ranging from 806.46 to 809.07 kg/m²·s for dry matter.

Table 2 and figures 1 and 2 show the results of the fluorination and desulphurization of EPA at the Central Kyzylkum WRPC.

Unlike the use of calcium carbonate in acid cleaning, the use of UCFC increases the amount of P₂O₅ in EPA from 19.85-20.15% to 20.15-21.89%, the formation of calcium fluoride is 120-150% and the formation of calcium sulphate. The amount of CaO in the acid is 1.26-2.15%, the amount of MgO and SO₃ is practically unchanged and the amount of fluorine in the acid is reduced to 0.31%.

Figures 1 and 2 present comparative data on fluoridation and desulphurization levels of calcium carbonate and WRPC. The figures show that with a normal calcium carbonate of 100-120% the fluorination level is 2.2-2.4% higher than that of WRPC and the sulphate level is 1.7-2.3% lower.

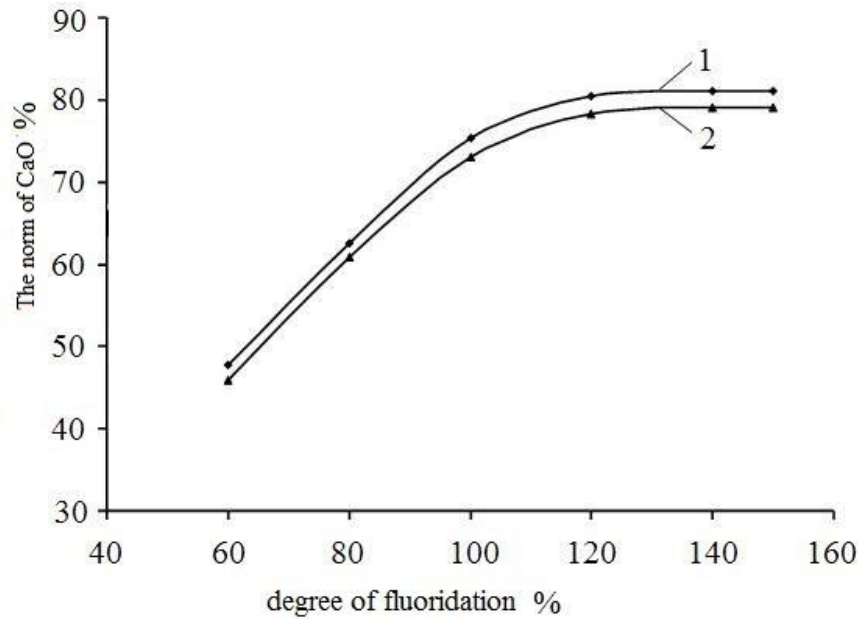


Figure.1. Effects of calcium carbonate (1) and UCFC (2) levels on fluorination

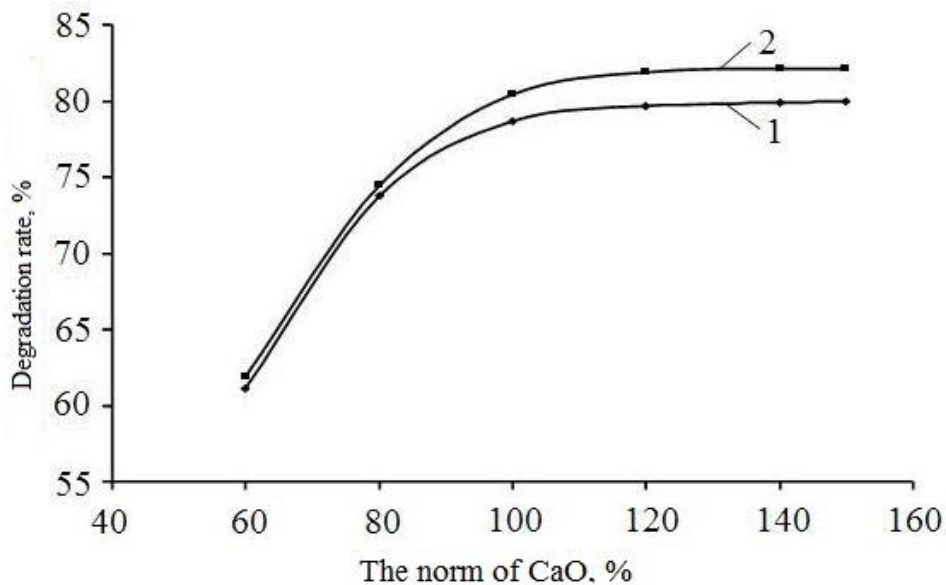


Figure.2. Effects of calcium carbonate (1) and UCFC (2) levels on sulphate levels.

Based on the research, a material balance of purification of fluorine and sulphate in the production of extractive phosphate acid from washed phosphate concentrate of Central Kyzylkum was developed (Figure 3). Production of high-quality concentrated phosphorus fertilizers based on fluoride and non-sulphate EPA is ensured.

The technology of EPA production from fluorine and sulphates has been tested in the industrial production of OAO «Ammophos-Maksam» and a prototype of high-quality mineral fertilizer of ammophos is made from this acid. The difference between the cost of Class I and Class I is 94,000 sums per ton. The production of 100 thousand tons of fertilizer will produce an economic effect of 9.4 billion sum.

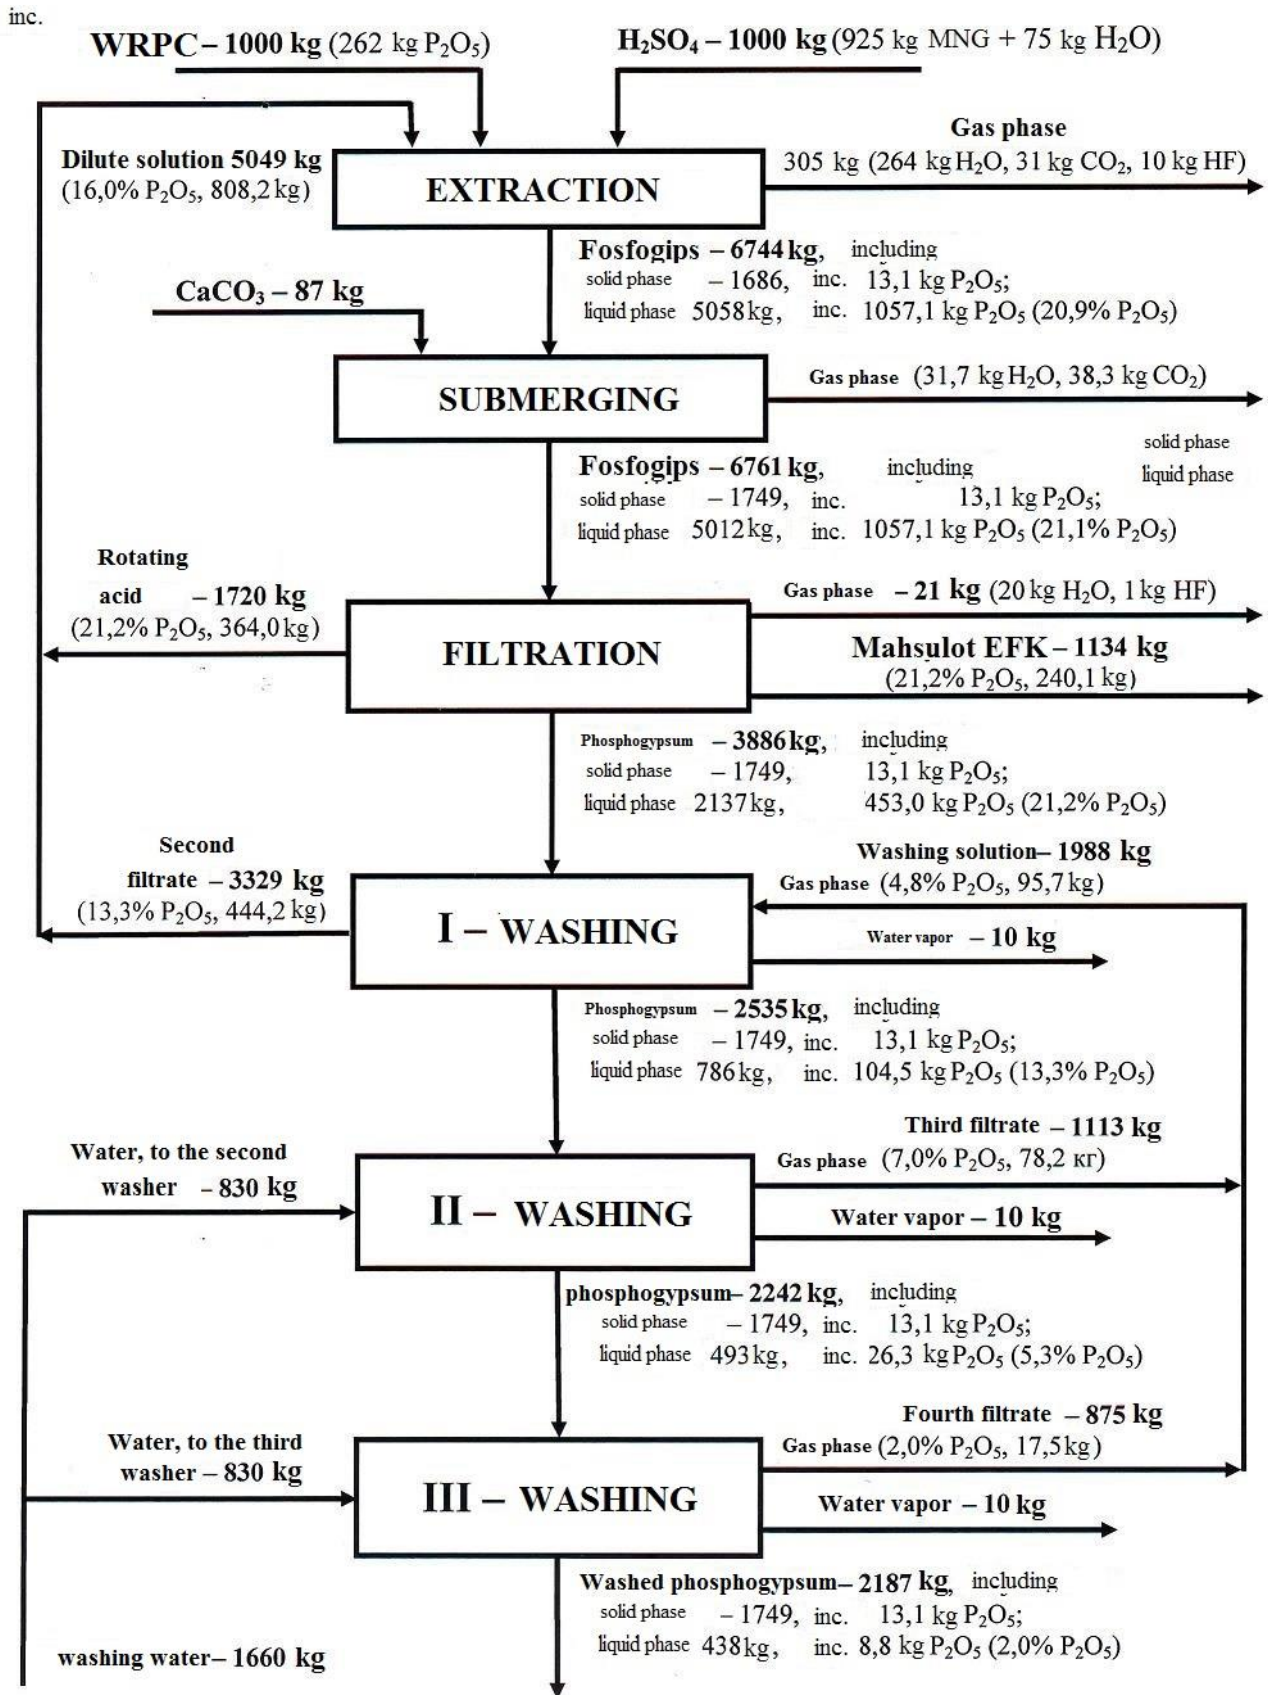


Figure 3. Material balance of production of EPA purified from fluorine and sulphate using carbonate feedstock

Adding calcium carbonate to the extraction solution solves three problems: partial discoloration and sulphate of extracted acid and calcium ion enrichment.

Ammonia with gaseous ammonia up to pH = 3.8-5.5 to obtain relatively pure solutions of pre-purified acid from fluorine and sulphate. Residual sulphates and fluorine are deposited with calcium ions as CaSO₄ and CaF₂, and iron and aluminium ions are deposited as FePO₄ and AlPO₄. The sediment is separated from the solution by decantation.

Table 3 shows the influence of ammonium level (pH) on the chemical composition of water-soluble ammonium phosphates.

table 3

Effects of ammonia level on the chemical composition of ammonium phosphates

pH	Chemical composition of ammonium phosphates, w. %				
	P ₂ O ₅	N	F	SO ₃	H ₂ O
3,8	56,91	11,54	0,11	0,24	1,43
4,5	58,63	12,83	0,03	0,08	2,54
5,2	59,95	13,71	0,01	0,04	2,18
5,3	58,81	14,03	0,01	0,03	2,27
5,5	57,48	14,21	0,01	0,02	1,34

When pH increased from 3.8% to 5.5, fluorine content decreased from 0.11% to 0.01% and sulphate from 0.24% to 0.02%, while P₂O₅ and nitrogen were 56.91% and 11.54% to 59.95% and 14.21%, respectively.

High-quality water-soluble ammonium phosphates can be obtained by partially purifying phosphoric acid during extraction and complete purification by extracting phosphoric acid with ammonia. The result is a simultaneous reduction of fluorine content from 0.11% to 0.01% and sulphates from 0.24% to 0.02% containing 56.91-59.95% P₂O₅ and 14.21-11.54%. A product with N was produced.

Conclusion. Studies have shown that simultaneous fluorination and desulphurization of EPA based on Central Kyzylykum phosphate can be achieved by adding calcium carbonate or WRPC to the extraction sludge. The optimal calcium carbonate and UFC levels are 100-120% for calcium fluoride and 100% for calcium sulphate. The sulphate content decreases from 2.22% to 0.44-0.48%, the fluorine content decreases from 1.32% to 0.25-0.30%, the rate of conversion of fluorine to the gas phase by extraction from 5.4% to 4%, and the rate of transition to phosphogypse increases from 40.5% to 82.5% to 85.7%. After purification from fluorine and sulphate, ammonium contains not more than 0.8-1.0% fluorine and more than 52.0% P₂O₅. The net profit from the conversion of refined EPA to ammonium is not less than 52.0% of P₂O₅ in the amount of 100,000 tonnes. Tonnes is 9.4 billion Sum.

High-quality water-soluble ammonium phosphates can be obtained from Central Kyzylykum phosphates by partial purification by phosphoric acid extraction and complete purification by the extraction of phosphoric acid with ammonia. The result is a simultaneous reduction of fluorine from 0.11% to 0.01% and sulfates from 0.24% to 0.02%, containing 56.91-59.95% P₂O₅ and 14.21-11.54%. A product with N was obtained. The products are integrated water-soluble nitrogen-phosphorus fertilizers that are used to grow crops by drip irrigation and hydroponics.

References

1. Ангелов А.И. Левин Б.В., Классен П.В. Мировое производство и потребление фосфатного сырья // Горный журнал. – Москва, 2003. – № 4-5. – С. 6-11.

2. «2017-2021 йилларда Ўзбекистон Республикасини ривожлантириш-нинг бешта устувор йўналиши бўйича Ҳаракатлар стратегияси» тўғрисидаги Ўзбекистон Республикаси Президентининг 07.02.2017 йилдаги ПФ-4947 сонли Фармони. – Тошкент. 2017.
3. Мамуров Б.А., Шамшидинов И.Т., Усманов И.И., Кодирова Г.К. Исследование процесса нейтрализации экстракционной фосфорной кислоты мелом. *Universum: Химические науки: электрон. научн. журн.*, 2019. – № 2(57). – С. 21-26.
4. G'afurov Q., Shamshidinov I. *Mineral o'g'it ishlab chiqarish nazariyasi va texnologik hisoblari*. – T.: Fan va texnologiya, 2010. – 360 b.
5. Shamshidinov I.T. *Noorganik moddalar va mineral o'g'itlar texnologiyasi: Darslik*. – T.: IQTISOD-MOLIYA, 2014. – 324 b.
6. Национальный доклад о состоянии окружающей среды и использовании природных ресурсов в Республике Узбекистан (1988-2007). – Ташкент, 2008. – 298 с.
7. Степень и экономические последствия фторидного загрязнения. *Обзорная информация*. – Обнинск, 1983. – Вып.1. – 55 с.
8. Васяев Г.В., Шевченко Т.П. О содержании фтора в урожае // *Записки Ленинградского с-х. ин-та*. – Л.: Изд-во ЛСХИ, 1974. – Т. 218. – С.10-18.
9. Халитов А.Х., Розин В.И. О необходимости исключения фтора из состава минеральных удобрений / В кн. *Интенсификация сельскохозяйственного производства и проблемы защиты окружающей среды*. – М.: Наука, 1980. – 296 с.
10. Хужамкулов С.З., Меликулова Г.Э., Мирмусаева К.С., Мирсаидов М.Х., Мирзакулов Х.Ч. Исследование процессов получения кремнефторида натрия из экстракционной фосфорной кислоты на основе фосфоритов Центральных Кызылкумов // *Химическая технология. Контроль и управление*. – Ташкент: ТГТУ, 2016. – № 1(67). – С. 34-40.
11. *World Fertilizer trends and Outlook to 2018*. Food and Agriculture Organization of the United Nations. Rome, FAO, 2015. – P. 55.
12. Зайцев В.А., Родин В.И. Влияние фтора на организм животных // *Журн. ВХО им. Д.И.Менделеева*, 1979. – Т. 24. – № 1. – С. 42-47.
13. Кочетков С.П. Смирнов Н.Н., Ильин А.П. Концентрирование и очистка экстракционной фосфорной кислоты. – Иваново: ГОУВПО Иван. гос. хим.-технол. ун-т, 2007. – 304 с.
14. Усербаетова Д., Тоиров З.К., Эркаев А.У., Каипбергенов А.Т. Обессульфачивание и очистка от примесей экстракционной фосфорной кислоты из фосфоритов Центральных Кызылкумов. // *Химия и химическая технология*. – Ташкент: ТХТИ, 2010. – № 2. – С. 2-4.
15. Хужамкулов С.З., Асамов Д.Д., Бардин С.В., Мирзакулов Х.Ч. Обесфторивание экстракционной фосфорной кислоты солями натрия. // *Химия и химическая технология*. – Ташкент: ТХТИ, 2008. – № 2. – С. 16-19
16. Хужамкулов С.З., Асамов Д.Д., Бардин С.В., Мирзакулов Х.Ч. Обесфторивание экстракционной фосфорной кислоты Центральных Кызылкумов в присутствии силиката натрия. // *Химия и химическая технология*. – Ташкент: ТХТИ, 2008. – № 4. – С. 8-11
16. Хужамкулов С.З., Асамов Д.Д., Бардин С.В., Мирзакулов Х.Ч. Разработка технологии обесфторивания экстракционной фосфорной кислоты Центральных Кызылкумов с рециклом силиката натрия. // *Кимёвий технология. Назорат ва бошқарув*. – Тошкент: TDTU, 2008. – № 4. – С. 41-45
17. Арифджанова К.С., Хужамкулов С.З., Нормуродов Б.А., Шамаев Б.Э., Мирзакулов Х.Ч. Обессульфачивание экстракционной фосфорной кислоты из

фосфоритов Центральных Кызылкумов необогащенным фосфатным сырьем // Кимёвий технология. Назорат ва бошқарув. – Тошкент: TDTU, 2016. – №3. – С. 32-39.

18. Мирмусаева К.С. Разработка технологии производства ортофосфатов натрия на основе экстракционной фосфорной кислоты Центральных Кызылкумов. Дис. на соискание ученой степени канд. техн. наук. – Ташкент. – 2011. – 156 с.

19. Патент № IAP 05054 UZ. МКИ С05 В3/00, С05 В11/00. Способ получения кормового преципитата. / Х.Ч.Мирзакулов, И.И.Усманов, Б.Б.Садыков, Н.В.Волынскова, Г.Э.Меликулова, Ш.И.Умаров, Оpubл. 31.07.2015. Бюл. № 7.

20. Геология и полезные ископаемые Республики Узбекистан / Т. Н. Долимов, Т. Ш. Шаякубов и др.: Редкол.: Т. Ш. Шаякубов (гл. ред.) и др. – Т.: Университет, 1998. – 724 с.

MODERN METHODS FOR MODIFICATION OF PHENOL-FORMALDEHYDE OLIGOMERS

Jabbarov Toxirjon Abdukodir ugli

Assistant of Namangan Institute of Engineering and Technology

Abstract:

Objective. *The process of interaction of a polyether polyol with a phenol-formaldehyde or furfuryl oligomer has been studied by IR spectroscopy. The formation of a co-oligomer as a result of the polycondensation reaction of polyether polyols with phenol alcohol has been proven. Currently, the demand for the synthesis of phenol formaldehyde oligomers is declining. This is due to difficulties in the use of phenol formaldehyde oligomers. As a result of the research, modified samples of phenol formaldehyde were synthesized.*

Results. *When the synthesized modified phenol formaldehyde resin was tested using the infrared spectrum, it was confirmed that its composition was indeed a new composition.*

Conclusion. *The results show that the properties of modified phenol formaldehyde oligomers need to be adjusted and their synthesis processes need to be optimized. The result is a new type of high-temperature composite material.*

Keywords: *modified phenol-formaldehyde oligomers, molar ratio, thermosetting oligomer, infrared spectroscopy.*

Introduction. The modern development of science and technology, proceeding from the existing problems in various industries and the national economy, contributes to the development of research on the latest technologies for the production of materials and products based on local raw materials, as well as cheaper import-substituting products. In the field of chemical production of polymer materials, the development of methods for studying the problems of chemical interaction of products obtained by synthesizing phenol and its derivatives with formaldehyde with other substances with the formation of new compounds is of great interest.

In the interaction of formaldehyde with phthalide-containing phenols and their mixtures with phenol in the presence of an acid catalyst, new phthalide-containing homo- and co-oligophenol-formaldehyde novolaks, phthalide-containing cross-linked homo- and copolymers based on them, were obtained, and their physicochemical properties were also studied [1]. Phenol-formaldehyde oligomers are well modified by joint polycondensation of phenol and formaldehyde with other monomers, in particular, with tert-butyl-N-phenylcarbamates. In their joint polycondensation, a mixture of three or more monomers is used, if each of them does not

CONTENTS

<u>PRIMARY PROCESSING OF COTTON, TEXTILE AND LIGHT INDUSTRY</u>	
<i>Kh.Kh.Rakhmonov, Sh.H.Behbudov, A.B.Nizomov.</i> Foreign experiences of light industry development in global competition and its implementation in Uzbekistan.....	2
<i>Sh.F.Imomaliyeva, A.M.Makhkamov.</i> Pressure loss on cotton air transport pipelines.....	5
<i>M.N.Mirzaahmedova, J.N.Mirzaaxmedov, K.M.Xoliqov.</i> Application of embroideral elements in modern women's clothes.....	10
<i>M.N.Salokhiddinova, R.M.Muradov.</i> A study to reduce the impact force in a cotton separator working chamber.....	14
<i>H.Yuldashev, A.Rakhmonov, A.Karimov.</i> Screening device detecting loose fibers in raw cotton, study the movement of the cotton ball inside the drum.....	19
<u>GROWING, STORAGE, PROCESSING OF AGRICULTURAL PRODUCTS AND FOOD TECHNOLOGIES</u>	
<i>A.T.Mamadaliyev.</i> Theoretical study of the movement of macro and micro fertilizers in aqueous solution after the seed falls from the spreader.....	26
<i>A.R.Umarov, A.K.Akhundadayev, G.M.Parpiyeva.</i> Research of the structure of genetic modified organisms (gmo) and ensuring food security in the modern world.....	31
<i>B.G'.Norinboyev, N.J.Jamoldinova.</i> Systematic analysis of processing of raw materials when obtaining powders and semi-finished products from agricultural products selection of optimal technological systems.....	37
<i>A.A.Halimboev.</i> Advances in storage of strawberry in controlled atmosphere storages.....	43
<i>M.F.Meliboyev, Sh.M.Mamatov, O.K.Ergashev, O.R.Qodirov.</i> Effects of the use of microwaves in sublimate drying.....	47
<i>X.Xoshimov, N.X.Xoshimova, D.A.Saribayeva, G.X.Raximova, Sh.X.Nuriddinov.</i> Improvement of technology of low calorie dietic confitures.....	51
<i>X.Xoshimov, N.X.Xoshimova.</i> The results of studies to determine the oil content and content of alilizotio cyanate of the sarepta mountain fox grown in the Namangan region.....	56
<i>J.B.Farmonov, Q.P.Serkaev, M.A.Samadiy.</i> Investigation of the influence of the pre-drying process on the extraction of oil from sesame seeds.....	60
<i>Sh.A.Sodikova, K.O.Dodaev.</i> Research of physicochemical parameters of sugar sorghum juices.....	64
<i>A.Kamalov, Z.Usmonova, M.Aliyeva, Q.G'aniyev.</i> Growing and adaptation of potato plants to the environment using in vitro technology.....	69
<u>CHEMICAL TECHNOLOGIES</u>	
<i>Kh.A.Makhammadjanov.</i> Thermal conductivity of polymer materials.....	72
<i>A.S.Arislanov, I.T.Shamshidinov, I.I.Usmanov.</i> Thermodynamic justification for the production of sulfur-containing nitrogen-phosphorus fertilizers.....	77
<i>A.S.Arislanov, I.T.Shamshidinov.</i> Removal of fluorine during the extraction of phosphoric acid.....	82

<i>D.N.Oljaev, T.I.Nurmurodov, I.N.Tursunova.</i> Research of processing of plastic physical activation of low-value phosphorites with acid salts.....	88
<i>U.Y.Raximov, D.J.Jumayeva.</i> Investigation of physico-chemical properties of thermally activated adsorbents on the basis of local waste.....	92
<i>A.U.Mamajonov, B.N.Abdullaev, L.M.Qosimov.</i> Features of the properties of cement systems in the presence of mineral fillers and additives of acetone-formaldehyde resin.....	99
<i>G.Q.Qodirova, I.T.Shamshidinov, Z.N.Mamadjanov, R.Y.Najmiddinov.</i> Purification of fluorine and sulphate impurities during the extraction of phosphoric acid and study of the process of obtaining high-grade ammonium phosphates.....	109
<i>T.A.Jabbarov.</i> Modern methods for modification of phenolo-formaldehyde oligomers.....	118
<i>O.Y.Ismailov, A.M.Khurmatov, O.T.Mallabayev.</i> Influence of recirculation of hydrocarbon flows on the efficiency of the heat exchanger operation.....	122
<i>T.U.Atamirzaev, N.M.Mallabaev.</i> Changes in the characteristics of the parameters of solar cells using protective coatings with thin frontal diffusion layers.....	129
<i>A.R.Umarov, Kh.Sh.Aripov, A.Mukhtorov, O.Kh.Makhmudjonova.</i> Development of the composition of reagents for drilling fluids.....	133
<i>S.S.Zokirov, Z.K.Dehkanov, D.Sh.Sherkuziev, Kh.Sh.Aripov, D.S.Isaboyeva.</i> Research of the process of neutralization of liquid fertilizers with monoethanolamine and their rheological properties.....	137
<i>A.M.Xurmatov, N.K.Yusupova, B.U.Obloyorbekov, M.X.Ismailov.</i> Physico-chemical properties of diluted oil sludge.....	141
<i>A.M.Xurmatov, N.K.Yusupova, B.U.Obloyorbekov, M.X.Ismailov.</i> Results of the output of light fractions when diluting oil sludge.....	145
<u>MECHANICS AND ENGINEERING</u>	
<i>S.O.Navruzov, A.A.Salomov, E.T.Muxametshina, M.M.Izatillayev, F.R.Asatov.</i> Improvement of the shaft-storage device for supplying to the cotton cleaning machine.....	150
<i>Sh.R.Fayzullayev, M.R.Raximberdiyev, H.T.Bobojanov, J.Z.Soloxiddinov.</i> The effect of the cylinder rotation frequency on the carding machine on the sliver and the yarn quality.....	157
<i>J.Z.Soloxiddinov, H.T.Bobojanov, Kh.K.Kakhkharova.</i> Analysis of the effect of spindle speed on the quality of yarn on the different ring spinning machines.....	163
<i>Sh.Kh.Abdazimov, A.M.Bashirova, G.R.Ibragimova, Sh.Sh.Kayumov.</i> To the question of improving the operating work of the load station in interaction with the access way of jsc "Uzbek steel works".....	170
<i>Sh.Abdazimov, B.I.Ismoilov, Sh.G.Musayev.</i> Protection against natural phenomena of transport structures and settlements of the republic of Uzbekistan.....	177
<i>E.S.Abdullaev, O.M.Kutbidinov, D.T.Yusupov, M.M.Rasulmukhamedov.</i> The importance of developing electronic registration systems and software block schemes for traction transformers.....	182
<i>A.Dj.Djurayev, J.Kh.Beknazarov, Sh.S.Chuliev.</i> Determination of gear extension parameters of a composite flexible element.....	190
<i>J.G.Rakhimov.</i> Technology of maintenance and repair of automobile electrical equipment....	195
<i>B.I.Negmatov, Q.J.Jumaniyazov, G.O.Kodirova.</i> Directions of improvement of cotton receiver - delivery mechanization means.....	202
<i>U.M.Muminov.</i> Methodology and research results of the developed fiber cleaner for determining the content of free fiber in waste.....	208

<i>A.S.Jumaev.</i> Calculation of downloads in component roller mechanisms belt conveyors.....	213
<i>Z.A.Khamrakulov, G.A.Doliev, A.B.Abdukhaev, O.G.Abdullaev, S.B.Mamazhanov.</i> Production of components for welding electrodes based on local raw materials.....	220
<i>N.E.Odilov.</i> Features of operation of gas-balloon engines.....	225
<i>A.A.Shermukhamedov, Kh.R.Baynazarov.</i> Dynamic calculation in the working process of the hydraulic cylinder of the unloading device of trailers.....	229
<i>A.A.Shermukhamedov, Kh.R.Baynazarov.</i> Equations of changes in the resistance force in the working process of the unloading device of trailers.....	236
<i>N.G.Bayboboev, A.A.Tursunov, U.G.Goyipov, Sh.B.Akbarov.</i> Calculation of chain transmission of a drum with elastic fingers of potato harvesters.....	242
<i>Sh.A.Suvankulov.</i> Production, purification and utilization of biogas as fuel for internal combustion engine.....	247
<i>A.A.Khudayberdiev, A.M.Khurmamatov, A.A.Khudaiberdiev.</i> Technical and economic aspects of processing pyrolysis distillate into motor fuel.....	252
<u>ADVANCED PEDAGOGICAL TECHNOLOGIES IN EDUCATION</u>	
<i>A.M.Kasimakhunova, M.A.Shakhodjaev.</i> The effectiveness of interactive methods in teaching solar energy in higher and vocational educational institutions.....	260
<i>Q.Sotivoldiev.</i> Structural features of physical culture classes and sports health classes in higher education institutions.....	264
<i>A.Khakimov.</i> The development of distance learning is a requirement of the times.....	268
<i>R.Usmanov, E.D.Imamnazarov.</i> Statistical filtering of pulse noise.....	270
<i>Sh.S.Djuraev, A.M.Jabborov, R.N.Sharifbaev.</i> Formation of statistics of students' follicles in higher education.....	276
<u>ECONOMICAL SCIENCES</u>	
<i>A.M.Arifjanov, I.G.Axmedov, D.E.Atakulov, I.I.Umarov.</i> Innovative technologies in evaluation of processes in bank.....	282
<i>R.A.Rashidov, A.B.Rustamov.</i> The importance of digital payment systems in the digital economy.....	287
<i>B.O.Tursunov.</i> Main directions of financial security in the enterprises of the textile industry of Uzbekistan.....	294



FOR THE AUTHORS!

Required criteria for submitted articles:

Articles can be only in English.

At the top of the first page should be given information about the author (authors) (last name, first name, middle name, place of work and position, scientific degree, e-mail, phone number).

Articles should be submitted in electronic and printed versions, signed by the author (s). The article should be organized as follows: no less than 5 sheets, in A4 format, in the range of 1.0, above, on the right, on the left, on the bottom, leave 2.5 cm, in the MS-WORD 2003-2010 program, at 12 pt. font Times New Roman.

This article in a particular specialty should be provided along with the official review of the doctor of science in the field of study and the act of examination of the possibility of publishing the article. At the same time, the editors have the right to require the provision of additional information from the authors and submit for additional expertise, on the basis of the results of which the issue of publishing the article will be decided.

Responsibility for the accuracy of information, facts and statistics is only the author of the article, the editors are not responsible.

The article must necessarily contain the exact sources of the tables (drawings, diagrams), the meaning of the abbreviated words must be explained.

Annotation of the article the purpose, methods, results and conclusions of the article should be summarized in the summary of the article.

Footnotes in the article should be listed as - [I]. At the end of the article, the list of references should be written in order of sequence. Scientific articles are printed in the order in which they are received by the editor. Articles that do not meet the above requirements of the editors are not considered.

The copyrights of scientific articles are protected by the Law "On Copyright and Homogeneous Rights" adopted on July 20, 2006.

Scientific articles are provided for publication after registration according to the requirements given in the "Terms of Submission of Articles". A scientific article with a signature on the last page must be submitted to the scientific department (3-building, 4-floor, left side 1-room).

Payment is made through the settlement account given below.

The settlement account of the Namangan Institute of Engineering and Technology:

Namangan, st. Kasansay, house number 7. Index: 160115. Fax: 225-10-07
Republic of Uzbekistan Ministry of Finance Treasury HKKM IB Tashkent city
23402000300100001010 MFO 0014 TIN 201122919
R.ZH 4001 1086 0144 0179 5010 0079 003
OKONH: 92110 INN: 200055908
Purpose of payment: you must specify "for the article on the NTZh"
E-mail: scientific_journal@mail.ru

Technical editor: Qodirov O.



**“SCIENTIFIC AND TECHNICAL JOURNAL OF
NAMANGAN INSTITUTE OF ENGINEERING AND
TECHNOLOGY”**



**The editorial was typed and paginated in the computer center
Paper format A4. Size 19.18 conditional printing plate**

**The copy must be taken from the "Scientific and Technical Journal of the
Namangan Institute of Engineering and Technology"**